

Synthesis and Characterization of Zeolite Obtained from Natural Kaolinite in the Jabal Nafusah, Libya

Dr. Rebie M. N. Jalah,

Tripoli University, Faculty of Education-Janzour Department of Chemistry,

Tripoli, Libya

Abstract

Zeolite NaA materials were synthesized successfully by hydrothermal method using the Jabal Nafusah kaolinite. In the first step, kaolinite [20g,125 μ m-particle size] has been calcined at 600 °C for 2h. confirm the transformation to the metkaolinite phase which has been detected during the calcination process in muffel funnece. As a second step, the zeolitisation experiments have been carried out under hydrothermal conditions. The metkaolinite obtained has been reacted with 200 ml of NaOH solutions of different concentrations in autoclaves /reflex at 105 °C for 2 h. The reaction product was found to be essentially sodium metakaolinate with the NaOH solution of 4 N. In third step filtration- filter the sodium metakaolinate and then dry. Prepaton of sodium silicate- take 5 grams of NaOH and 5 grams of Sio2 in 25ml of distilled water, heat and stir the contents gently. Prepaton of sodium aluminate - take 5 grams of NaOH and 5 grams of Al(OH)3 in 25ml of distilled water, heat and stir the contents gently mixing of sodium silicate and sodium aluminate until optimum solubility , in the fourth step-thermal-method; heat the mixture of sodium metakaolinate, sodium silicate, and sodium aluminate at 600 °c for 2 h the products obtained from the experiments have been characterized by using infrared spectroscopic, x-difraction analysis and electron microscope methods. Zeolite NaA can be obtained from kaolinite under the conditions applied showing that a metakaolinitisation can be achieved at 600 °C which is much lower than the temperatures given in the literature, 700-900 °C and also the time necessary for formation of zeolite NaA is less than that of the previous works.

Keywords: *Zeolite NaA; Kaolinite; Characterization Synthesis; hydrothermal synthesis; X-ray diffraction*

INTRODUCTION

The paper industry generates a significant amount of solid wastes requiring appropriate disposal. Zeolites are crystalline, microporous, hydrated aluminosilicates of alkaline or alkaline earth metals. The frameworks are composed of $[\text{SiO}_4]_4$ and $[\text{AlO}_4]_5$ tetrahedra, which corner-share to form different open structures. Negative charge of lattice is compensated by the positive charge of cations located at specific positions of zeolite framework (Bekkum et al., 1991; Breck, 1974). In most of zeolites the compensating cations are usually mono- and bi-valent metal ions and/or their combinations (e.g. Engelhardt and Michel, 1987; Takaishi et al., 1995; Earl and Deem, 2006). In accordance with the Loewenstein's rule (Loewenstein, 1954), Al-O-Al bonds do not exist in aluminosilicate frameworks of zeolite. Instead of the tetrahedrally bonded atoms Si and Al, so-called "T-atoms", others such as P, Ga, Ge, B, Be, etc. can exist in the framework as well (McCusker and Baerlocher, 2001; Takaishi et al., 1995). The synthesis of zeolites in forms suitable for industrial applications is of great importance. The first synthesis of zeolite was attempted by St. Claire-Deville in 1862. Barrer's pioneering work in 1948 demonstrated that a wide range of zeolites could be synthesized from aluminosilicate gels.

At present, synthetic zeolites are used commercially more often than natural zeolites due to the purity of crystalline products and the uniformity of particle sizes (Breck, 1974; Szoztak, 1998). However, the preparation of synthetic zeolites from chemical sources of silica and alumina is expensive. Such costs may be reduced by the use of clay minerals, volcanic glasses (perlite and pumice), rice husks, diatoms, fly ash or paper sludge ash as starting materials (e.g. Adamczyk and Bialecka, 2005; Querol et al., 1997; Saija et al., 1983; Tanaka et al., 2004; Walek et al., 2008; Wang et al., 2008). Zeolite has also been developed by the transformation of one zeolite type into other zeotypes (Rios et al., 2007; Sandoval et al., 2009).

Previous work has shown that kaolin is not stable under highly alkaline conditions and different zeolitic materials can form, and that kaolin is usually used after calcinations

to obtain a more reactive phase (metakaolin). After dehydration (endothermic dehydroxylation), kaolin is transformed into amorphous metakaolin (Fialips, 1999; Gougazeh and Buhl, 2010; Smykatz-Kloss, 1975). Raw kaolin and metakaolin have been used as the Al and Si sources for synthesis of zeolite Linde Type A, X, Y, P, 4A, NaA, KI, cancrinite, sodalite, hydroxysodalite, faujasite, phillipsite, chabazite and several other types of zeolites (e.g., Buhl and Loens, 1996; Covarrubias et al., 2006; Dudzik and Kowalak, 1974; Gualtieri et al., 1997; Lin et al., 2004; Loiola et al., 2012; Marcelo et al., 2007; Mon et al., 2005; Rees and Chandrasekhar, 1993; Sanhueza et al., 1999; Vilma et al., 1999; Zhao et al., 2004).

NaA Zeolite is of great industrial importance due to its molecular sieving, ion exchange and water adsorption properties. With the molar ratio Si/Al nearly equal to one, kaolin is an ideal raw material for preparing NaA zeolite. Kaolin was one of the most versatile industrial minerals and was used extensively for many applications (Murray, 1991). The synthesis of NaA zeolite from kaolin source was started from the 1970s (Breck, 1974; Barrer, 1978) by the hydrothermal reaction of dehydroxylated kaolin with sodium hydroxide solution.

No attempt has been made previously to produce zeolite type A from natural Jordanian kaolin. In this work, Zeolite A was hydrothermally synthesized from Jordanian kaolin, and the effect of NaOH concentration (1.0, 1.5, 2.0, 2.5, 3.5 and 4 M NaOH) was investigated. The synthesized products were characterized by X-ray diffraction (XRD) scanning electron microscopy (SEM) and Fourier transform infrared (FTIR) spectroscopy.

RESULTS AND DISCUSSION

The kaolin used was fully characterized (mineralogical and chemical composition, thermal behavior and particle size distribution) and the results were similar with previous study by Gougazeh and Buhl (2010). The grain size analysis of bulk kaolin sample was separated by Atterberg methods. The quantitative analysis of the mineral content of the natural Jabal

Nafusah in Libyan kaolin has been worked out by a combination of XRD and XRF investigations. The physical, chemical and mineralogical properties of the kaolin under study are presented in Table 1 with Figure 1-6. The XRD pattern of metakaolin obtained by heating the kaolin for 3 h at 650° C resembled others, except for the peaks due to admixed impurities. The properties of the reaction intermediates and products were determined by various techniques to give the following results.

Results on the graphic and phase identification of the sample#0.09 mic on Figure 1 and semi quantitative analysis (see Table A1).

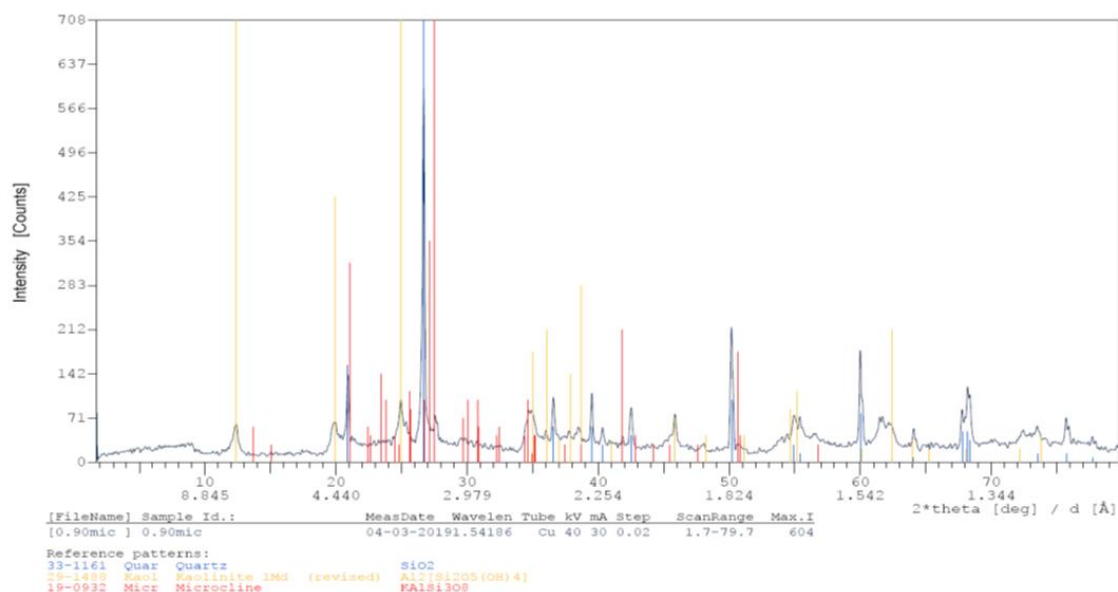


Figure 1. XRD patterns of quartz, kaolinite and, microcline and associated phases obtained by hydrothermal synthesis.

Table A1: Properties of Jabal Nafusah kaolin on Figure 1.

Phase%	SUM	Quar	Kaol	Micr
	100.00	23.23	32.71	44.06
K ₂ O%	7.46			7.46
SiO ₂ %	66.99	23.23	15.22	28.54
Al ₂ O ₃ %	20.99		12.92	8.07
H ₂ O%	4.56		4.56	
LOI %	4.56	0.00	4.56	0.00

Results on the graphic and phase identification of the sample#0.75 mic on Figure 2 and semi quantitative analysis (see Table A2).

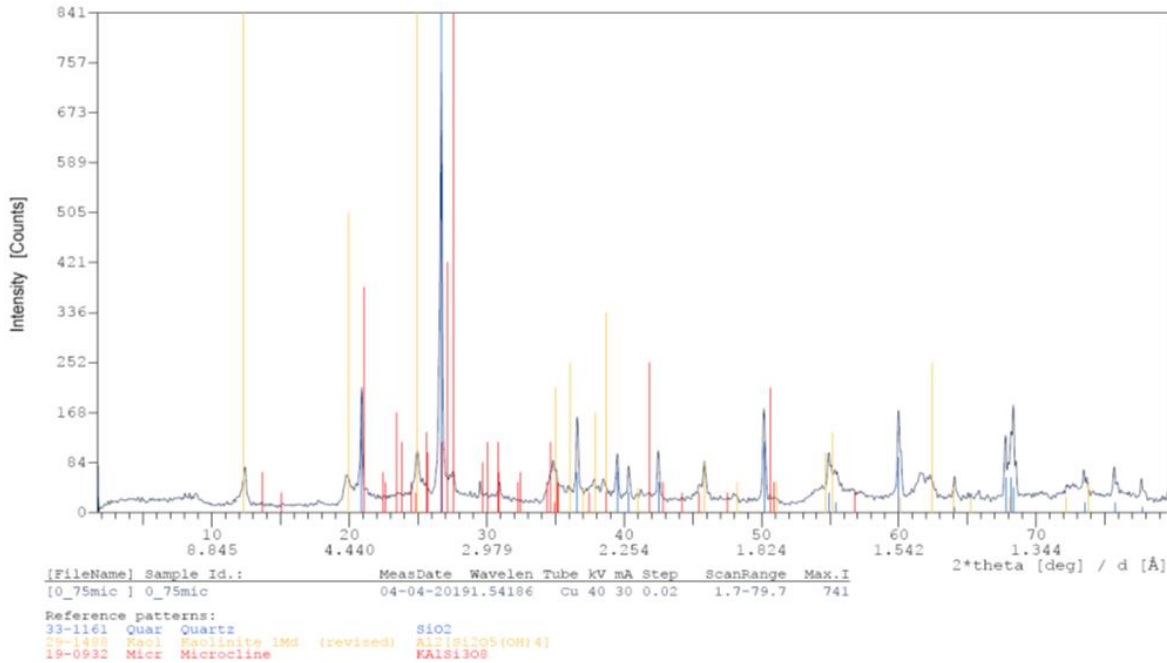


Figure 2. XRD patterns of quartz, kaolinite and, microcline and associated phases obtained by hydrothermal synthesis.

Table A2: Properties of Jabal Nafusah kaolin on Figure 2.

Phase%	SUM	Quar	Kaol	Micr
	100.00	24.73	29.70	45.56
K₂O%	7.71			7.71
SiO₂%	68.07	24.73	13.83	29.51
Al₂O₃%	20.08		11.73	8.35
H₂O%	4.15		4.15	
LOI %	4.15	0.00	4.15	0.00

Results on the graphic and phase identification of the Sample#125 mic on Figure 3 and semi quantitative analysis (see Table A3).

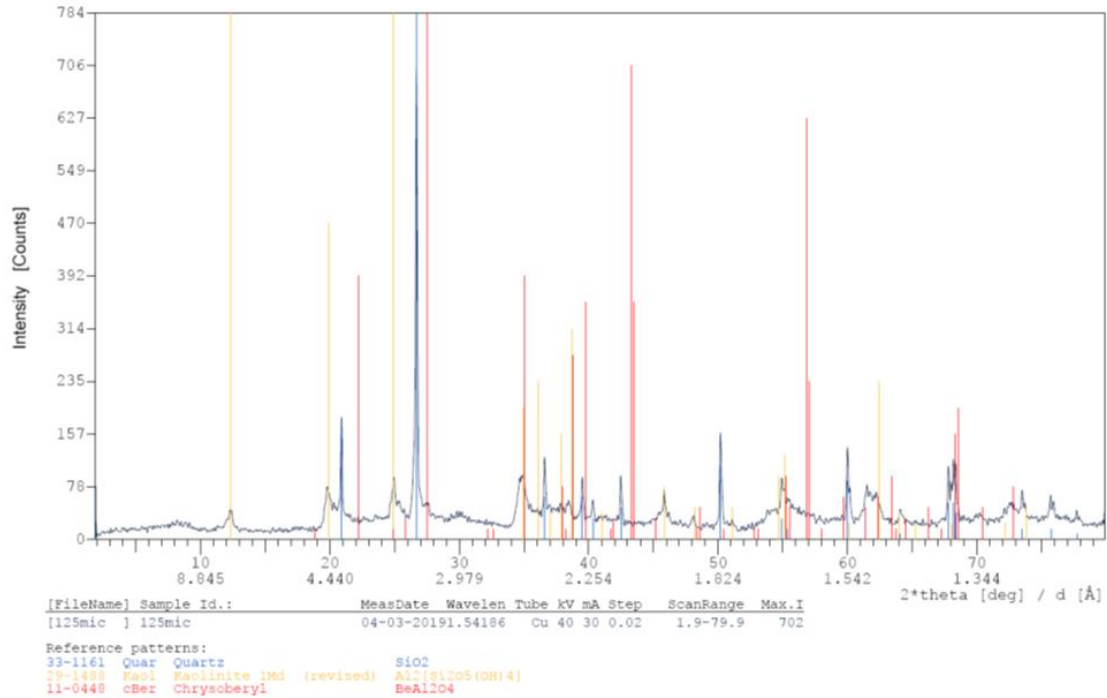


Figure 3. XRD patterns of quartz, kaolinite and, chrysoberyl and associated phases obtained by hydrothermal synthesis.

Table A3: Properties of Jabal Nafusah kaolin on Figure 3.

Phase%	SUM	Quar	Kaol	cBer
	100.00	27.84	39.59	32.57
SiO₂%	46.27	27.84	18.43	
Al₂O₃%	41.79		15.64	26.15
BeO%	6.42			6.42
H₂O%	5.53		5.53	
LOI %	5.53	0.00	5.53	0.00

Results on the graphic and phase identification of the sample#355 mic on Figure 4 and semi quantitative analysis (see Table A4).

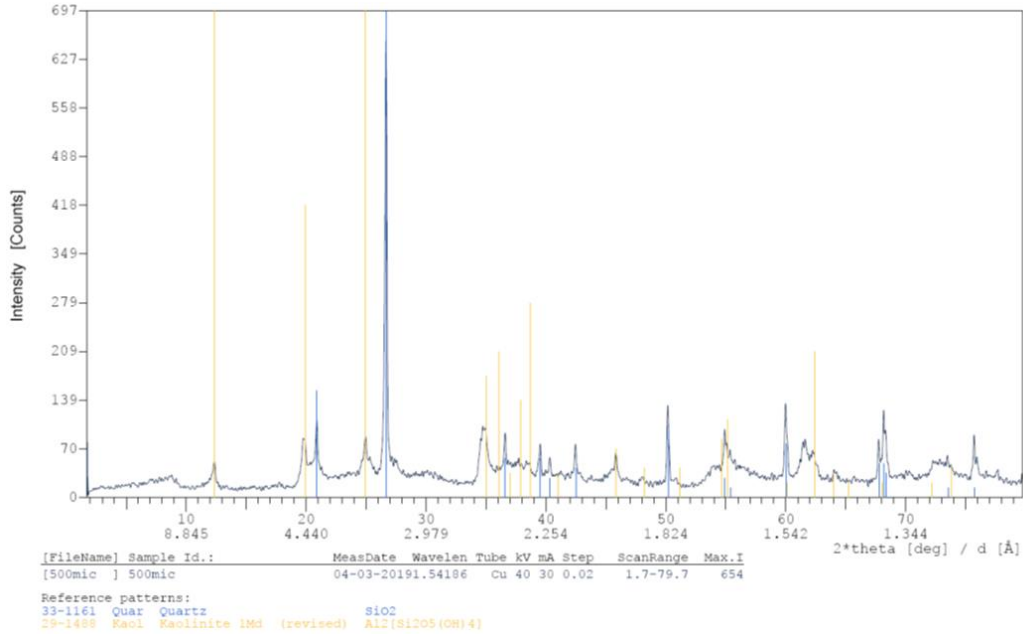


Figure 4. XRD patterns of quartz and, kaolinite and associated phases obtained by hydrothermal synthesis.

Table A4: Properties of Jabal Nafusah kaolin on Figure 4.

Phase%	SUM	Quar	Kaol	Tlr
	100.00	35.20	51.74	13.07
TeO₃%	17.98			17.98
SiO₂%	59.28	35.20	24.08	
Al₂O₃%	20.43		20.43	
H₂O%	7.22		7.22	
LOI %	2.30	0.00	7.22	-4.92

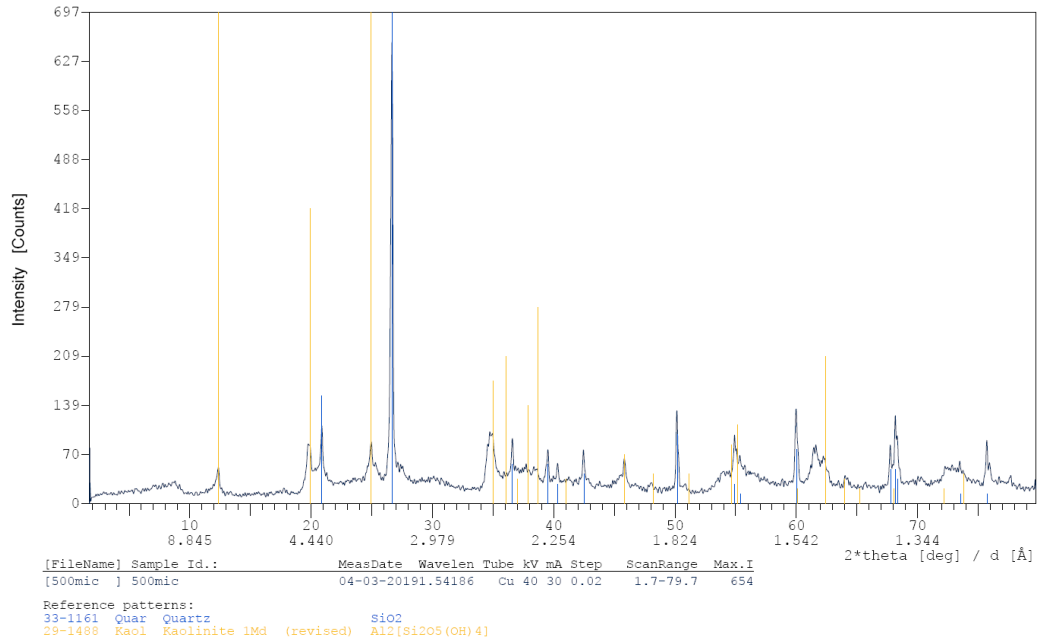


Figure 5. XRD patterns of quartz and, kaolinite and associated phases obtained by hydrothermal synthesis.

Results on the graphic and phase identification of the sample#500 mic on Figure 5 and semi quantitative analysis (see Table A5).

Table A5: Properties of Jabal Nafusah kaolin on Figure 5.

	SUM	Quar	Kaol
Phase%	100.00	39.46	60.54
SiO ₂ %	67.64	39.46	28.18
Al ₂ O ₃ %	23.91		23.91
H ₂ O%	8.45		8.45
LOI %	8.45	0.00	8.45

Results on the graphic and phase identification of the sample#600 mic on Figure 6 and semi quantitative analysis (see Table A6).

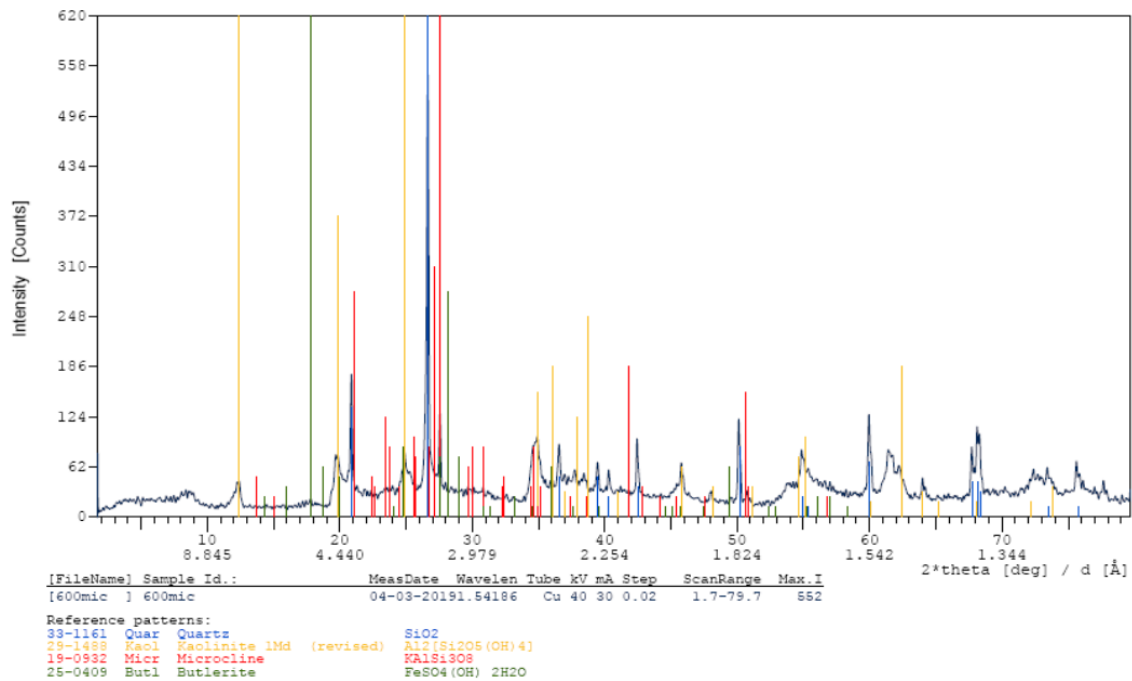


Figure 6. XRD patterns of quartz, kaolinite, microcline and, butlerite and associated phases obtained by hydrothermal synthesis.

Table A6: Properties of Jabal Nafusah kaolin on Figure 6.

Phase%	SUM	Quar	Kaol	Micr	Butl
100.00	100.00	12.57	20.22	28.13	39.07
Fe₂O₃%	15.22				15.22
K₂O%	4.76			4.76	
SO₃%	15.26				15.26
SiO₂%	40.21	12.57	9.41	18.22	
Al₂O₃%	13.14		7.99	5.15	
H₂O%	11.41		2.82		8.59
LOI %	26.67	0.00	2.82	0.00	23.85

CONCLUSIONS

Based on the results of XRD of zeolite produced by treating the activated metakaolin from natural Jabal Nafusah kaolin with various concentrations of NaOH at 600° C for 20 h, some observations could be summarized as follows:

- The results indicated that the obtained kaolinite products contain Zeolite NaA as the major constituent phase, whereas hydroxysodalite (HS) and quartz were found as minor phases. With one exception untransformed metakaolin occurred only in considerable amounts at 1.0 M NaOH. Although the amount of untransformed metakaolin probably decreases with increasing NaOH concentration. On the other hand, amount of HS increases with the increasing NaOH concentration, which could account for the decrease in the amount of zeolite.
- The synthesized products were found to contain quartz phases as impurities coming from the natural kaolin samples (see XRD pattern in Figure 1-6).
- Zeolite was hydrothermally synthesized using kaolin as the raw material. The XRD analysis confirmed an excellent relative crystallinity.
- For a future research we are going to evaluate the efficiency of such zeolite materials in selective cation exchange as ion exchangers, adsorbents and catalysts.

References

- Adamczyk, Z., Bialecka, B., 2005. Hydrothermal synthesis of zeolites from polish coal fly ash. *Pol. J. Environ. Stud.* 14 (6), 713–719.
- Barrer, R.M., 1978. *Zeolites and Clay Minerals as Sorbents and Molecular Sieves.* Academic Press, London.
- Bekum, V.H., Flanigen, E.M., Jacobs, P.A., Jansen, J.C., 1991. *Introduction to Zeolite Science and Practice*, 2nd revised Ed. Elsevier, Amsterdam.
- Breck, D.W., 1974. *Zeolite Molecular Sieves: Structure, Chemistry and Uses.* John Wiley, New York.

- Covarrubias, J.C., Garcia, R., Arriagada, R., Yanez, J., Garland, T., 2006. Cr (III) Exchange on Zeolites Obtained from Kaolin and Natural Mordenite. *Microporous Mesoporous Mater.* 88, 220–231.
- Dudzik, Z., Kowalak, S., 1974. Preparation of zeolites of faujasite type from kaolin. *Przemys'ł Chemiczny* 53, 616–618.
- Engelhardt, G., Michel, D., 1987. *High-Resolution Solid-State NMR of Silicates and Zeolites.* Wiley, New York.
- Gougazeh, M., Buhl, J.-C.h., 2010. Geochemical and Mineralogical Characterization of the Jabal Al-Harad Kaolin Deposit, Southern Jordan for its Possible Utilization. *Clay Miner. Mineral. Soc. Great Britain Ireland* 45 (4), 281–294.
- Gualtieri, A., Norby, P., Artioli, G., Hanson, J., 1997. Kinetic study of hydroxysodalite formation from natural kaolins by time resolved synchrotron powder diffraction. *Microporous Mater.* 9, 189–201.
- Lin, D.C., Xu, X.W., Zuo, F., Long, Y.C., 2004. Crystallization of JBW, CAN, SOD and ABW type zeolite from transformation of metakaolin. *Microporous Mesoporous Mater.* 70, 63–70.
- Lin, D.C., Xu, X.W., Zuo, F., Long, Y.C., 2004. Crystallization of JBW, CAN, SOD and ABW type zeolite from transformation of metakaolin. *Microporous Mesoporous Mater.* 70, 63–70.
- Loewenstein, W., 1954. *Am. Miner.* 39, 92.
- Loiola, A.R., Andrade, J.C.R.A., Sasaki, J.M., da Silva, L.R.D., 2012. Structural analysis of zeolite NaA synthesized by a cost-effective hydrothermal method using kaolin and its use as water softener. *J. Colloid Interface Sci.* 367, 34–39.
- Marcelo, L.M., Diego, I.P., Nadia, R.C., Fernandes. Machado, Sibebe, B.C., Pergher,, 2007. Synthesis of mordenite using kaolin as Si and Al source. *Appl. Clay Sci.* 41, 99–104.
- McCusker, L.B., Baerlocher, C., 2001. Zeolite structures. In: Van Bekkum, H., Flanigen, E.M., Jacobs, P.A., Jansen, J.C. (Eds.), *Introduction to zeolite science and practice*

- Studies in Surface Science and Catalysis, vol. 137. Elsevier, Amsterdam, pp. 37–65.
- Mon, J., Deng, Y., Flury, M., Harsh, J., 2005. Cesium incorporation and diffusion in cancrinite, sodalite, Zeolite, and allophone. *Microporous Mesoporous Mater.* 86, 277–286.
- Murray, H.H., 1991. Overview: Clay Mineral Application. *Appl. Clay Sci.* 5, 379–395.
- Querol, X., Plana, F., Alastuey, A., Lopez-Soler, A., 1997. Synthesis of Na-zeolites from fly ash. *Fuel* 76, 793–799.
- Rees, L., Chandrasekhar, S., 1993. Hydrothermal reaction of kaolin in presence of fluoride ions at pH less than 10. *Zeolites* 13, 534–541.
- Rios, C.A., Williams, C.D., Maple, M.J., 2007. Synthesis of zeolites and zeotypes by hydrothermal transportation of kaolinite and metakaolinite. *BISTUA* 5 (1), 15–26.
- Saija, L.M., Ottana, R., Zipelli, C., 1983. Zeolitization of pumice in ash-sodium salt solutions. *Mater. Chem. Phys.* 8, 207–216.
- Sandoval, M.V., Henao, J.A., Rios, C.A., Williams, C.D., Apperley, D.C., 2009. Synthesis and characterization of zeotype ANA framework by hydrothermal reaction of natural clinker. *Fuel* 88, 272–281.
- Sanhueza, V., Kelm, U., Cid, R., 1999. Synthesis of molecular sieves from Chilean kaolins: 1. Synthesis of NaA type zeolite. *J. Chem. Technol. Biotechnol.* 74, 358–363.
- Smykatz-Kloss, W., 1975. *Differential Thermal Analysis, Application and Results in Mineralogy.* Springer, New York.
- Szoztak, R., 1998. *Molecular Sieves: Principles of Synthesis and Identification*, 2nd ed. Blackie Academic and Professional, London, 359 pp.
- Takaishi, T., Kato, M., Itabashi, K., 1995. Determination of the ordered distribution of aluminum atoms in a zeolitic framework. Part II. *Zeolites* 15, 21–32.
- Tanaka, H., Miyagawa, A., Eguchi, H., Hino, R., 2004. Synthesis of a pure-form Zeolite A from coal fly ash by dialysis. *Ind. Eng. Chem. Res.* 43, 6090–6094.

- Treacy, M.J., Higgins, J.B., 2001. Collections of Simulated XRD Powder Patterns for Zeolites, 4th ed. Elsevier, Amsterdam, The Netherlands, 379 p.
- Walek, T.T., Saito, F., Zhang, Q., 2008. The effect of low solid/liquid ratio on hydrothermal synthesis of zeolites from fly ash. *Fuel* 87, 3194–3199.
- Wang, C.F., Li, J.S., Wang, L.J., Sun, X.Y., 2008. Influence of NaOH concentrations on synthesis of pure-form zeolite A from fly ash using two-stage method. *J. Hazard. Mater.* 155, 58–64.
- Zhao, H., Deng, Y., Harsh, J., Flury, M., Boyle, J., 2004. Alteration of Kaolinite to Canrinite and Sodalite by Simulated Hanford Waste and its Impact on Cesium Retention. *Clays Clay Miner.* 52 (1), 1–13.